

# Photoluminescence Study of Tin Oxide-Zinc Oxide Nanocomposites

K.J.Abhirama<sup>1\*</sup>, K.U.Madhu<sup>2</sup>

<sup>1,2</sup>Physics Research Centre, S.T.Hindu College, Nagercoil, Tamil Nadu, India  
(Affiliated to Manonmaniam Sundaranar University, Abishekapatti, Tirunelveli, 627012)

\*Corresponding Author: [abhiramathampi87@gmail.com](mailto:abhiramathampi87@gmail.com), Tel.: 04651-278910

Available online at: [www.isroset.org](http://www.isroset.org)

Accepted: 26/Jun/2018, Online: 31/Aug/2018

**Abstract-** Undoped and Cu<sup>2+</sup> doped (SnO<sub>2</sub>)<sub>1-x</sub>(ZnO)<sub>x</sub> nanocomposites were synthesized using a simple microwave assisted solvothermal method with ethylene glycol as solvent. The as-prepared samples were calcinated at 500 °C for 1hr. The optical studies were carried out using Photoluminescence measurements. A small shift in the peak position was observed for doped samples when compared to undoped samples. The shifting was due to the incorporation of dopant into the host matrix and also coupled with the variation of band gap energies of the nanocomposites. The results obtained were reported and discussed herewith.

**Key words:** Nanocomposite, Photoluminescence, Solvothermal, Tin oxide, Zinc oxide.

## I. Introduction

In the past three decades, nanostructured materials are considered as an exciting research area. Nanotechnology is an interdisciplinary area where the theories in Physics, Chemistry, Biology and Engineering are used to manipulate and design new devices. Nanomaterials are used as safer and efficient product in agriculture, industry, medicine, transport and communication [1]. SnO<sub>2</sub> and ZnO nanoparticles are used as sensors [2, 3, 4], solar cells [5, 6], catalyst [7, 8], antibacterial agent [9], in lithium ion batteries [10, 11] and so on. Luminescence is a phenomenon in which a material when excited with an external source like electrons, photons, etc will emit light in the visible range, UV or IR. The process in which a substance absorbs photons and get excited to a higher energy state and then return to lower energy state with the emission of another photon is termed as photoluminescence. SnO<sub>2</sub>-ZnO nanocomposites can be synthesized via sol-gel method [12-14], hydrothermal [15], co-precipitation method [16, 17], atomic layer deposition technique [18] and spray pyrolysis [19, 20]. The properties of the nanoparticles can be modified by the inclusion of suitable dopants into the parent matrix.

In the present work the photoluminescence studies were carried out for (SnO<sub>2</sub>)<sub>1-x</sub>(ZnO)<sub>x</sub> nanocomposites (with x values 0.0, 0.2, 0.4, 0.5, 0.6, 0.8 and 1.0). Different excitation wavelengths ranging from 272 nm to 335 nm were used to record the emission spectra. The results obtained were reported and discussed. This article is organized as follows: Section I gives the introduction about photoluminescence studies. Section II explains the experimentation and characterization of tin oxide- zinc oxide nanocomposites. The

results and discussions of the related work are discussed in section III and in the last section IV the conclusions of the research work are given.

## II. Experimentation and Characterization

Undoped and Cu<sup>2+</sup> doped (SnO<sub>2</sub>)<sub>1-x</sub>(ZnO)<sub>x</sub> nanocomposites (with x values 0.0, 0.2, 0.4, 0.5, 0.6, 0.8 and 1.0) were synthesized using a simple microwave assisted solvothermal method. The experimental procedure for the synthesis of undoped and Cu<sup>2+</sup> doped (SnO<sub>2</sub>)<sub>1-x</sub>(ZnO)<sub>x</sub> nanocomposites (with x values 0.0, 0.2, 0.4, 0.5, 0.6, 0.8 and 1.0) was explained in detail in our earlier work [21,22]. The as prepared samples were calcinated at 500 °C for 1hr. The photoluminescence measurements of calcinated samples were carried out at room temperature.

## III. Results and Discussion

The photoluminescence spectra of undoped and Cu<sup>2+</sup> doped (SnO<sub>2</sub>)<sub>1-x</sub>(ZnO)<sub>x</sub> nanocomposites are shown in Figures 1- 14. Undoped SnO<sub>2</sub> nanoparticles show two prominent peaks at 421 and 462 nm. The strong indigo peak at 421 nm was attributed to electron transition due to oxygen vacancies and defects in SnO<sub>2</sub> nanoparticles [23,24]. The strong blue emission peak at 462 nm was due to electron transition arbitrated by defect levels such as oxygen vacancies in the energy gap [25]. (SnO<sub>2</sub>)<sub>1-x</sub>(ZnO)<sub>x</sub> nanocomposites with x values (0.2, 0.4, 0.5, 0.6 and 0.8) show prominent peaks at 415 and 453 nm; 418 and 460 nm; 419 and 461 nm; 421 and 462 nm; 430 and 465 nm respectively. The strong violet peaks at 415, 418 and 419 nm and the strong indigo peaks at 421 and 430 nm are due to electron transitions arbitrated by defects levels in the band gap such as oxygen vacancies or tin

interstitials [23, 24]. The strong blue emissions at 453, 460, 461, 462 and 465 nm are due to electron transitions arbitrated by defect levels such as oxygen vacancies in the energy gap [25].

ZnO nanoparticles show four prominent peaks at 464, 502, 660 and 684 nm. The weak blue emission peak at 464 nm was ascribed to the transition between the shallow donor levels of zinc vacancies and the shallow acceptor levels of oxygen vacancies [26]. Also the excitons on the surface of ZnO nanoparticles give rise to emission peak around 465 nm [27]. The weak green emission peak at 502 nm was due to the presence of singly ionized oxygen vacancies and the recombination of photogenerated hole with the singly-ionized charge state results in green emission [28, 29]. The radioactive recombination of a photogenerated hole with an electron occupying the oxygen vacancy causes luminescence emission peak [30]. The occurrence of red emission peaks around 660 and 684 nm are attributed to deep level emission. Oxygen interstitial defects in ZnO nanoparticles paved way for deep level emission [31]. The peaks at 660 and 684 nm are highly intense and the reason for high peak intensity at this region is mainly due to the increase in the number of oxygen vacancies [32].  $\text{Cu}^{2+}$  doped  $(\text{SnO}_2)_{1-x}(\text{ZnO})_x$  nanocomposites show shift in the peak position when compared to undoped  $(\text{SnO}_2)_{1-x}(\text{ZnO})_x$  nanocomposites. The shifting was due to the incorporation of dopant into the host matrix and also coupled with the variation of band gap energies of the nanocomposites [33].

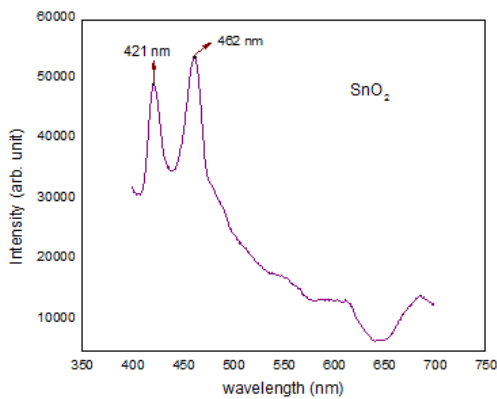


Figure 1: PL spectrum of SnO<sub>2</sub> nanoparticles

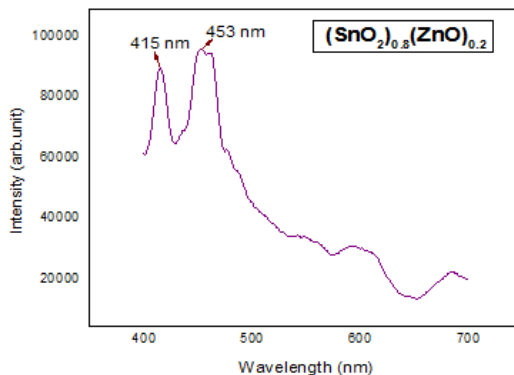


Figure 2: PL spectrum of  $(\text{SnO}_2)_{0.8}(\text{ZnO})_{0.2}$  nanocomposite

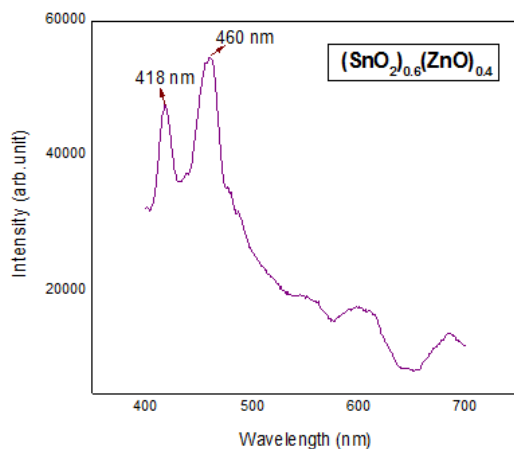


Figure 3: PL spectrum of  $(\text{SnO}_2)_{0.6}(\text{ZnO})_{0.4}$  nanocomposite

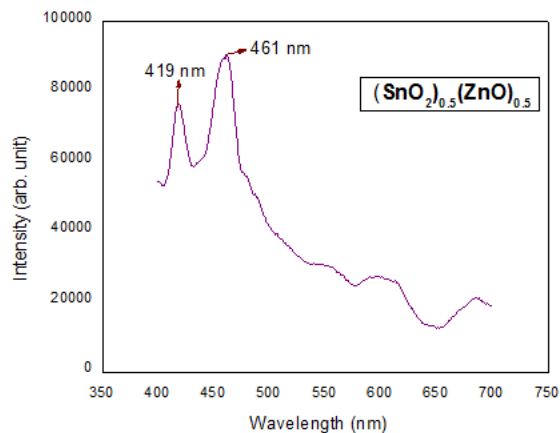


Figure 4: PL spectrum of  $(\text{SnO}_2)_{0.5}(\text{ZnO})_{0.5}$  nanocomposite

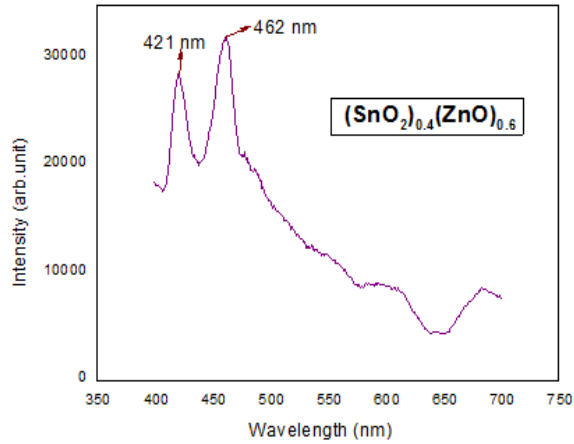


Figure 6: PL spectrum of  $(\text{SnO}_2)_{0.4}(\text{ZnO})_{0.6}$  nanocomposite

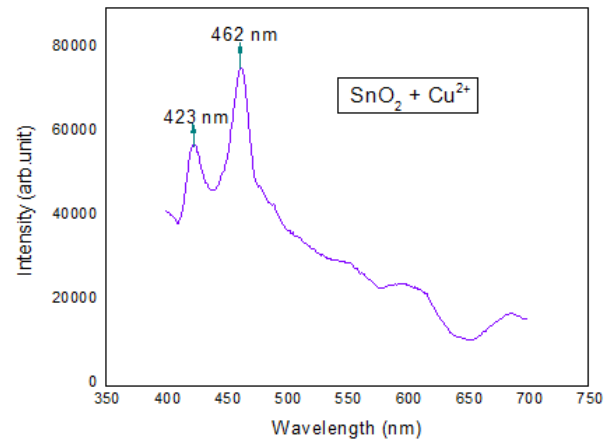


Figure 8: PL spectrum of  $\text{SnO}_2 + \text{Cu}^{2+}$  nanoparticles

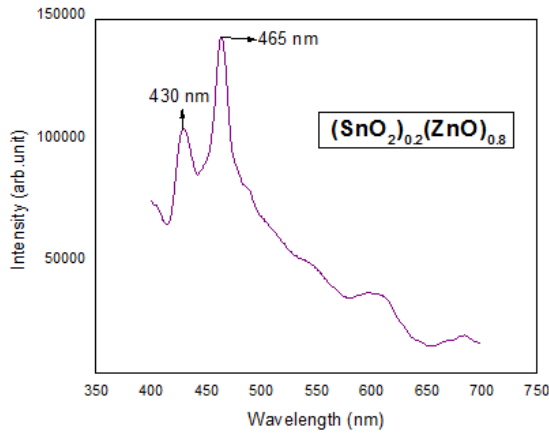


Figure 5: PL spectrum of  $(\text{SnO}_2)_{0.2}(\text{ZnO})_{0.8}$  nanocomposite

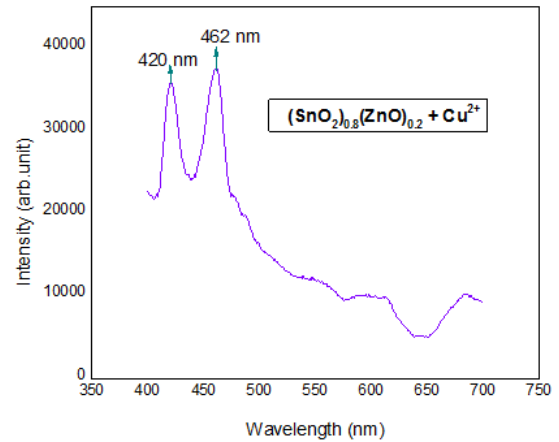


Figure 9: PL spectrum of  $(\text{SnO}_2)_{0.8}(\text{ZnO})_{0.2} + \text{Cu}^{2+}$  nanocomposite

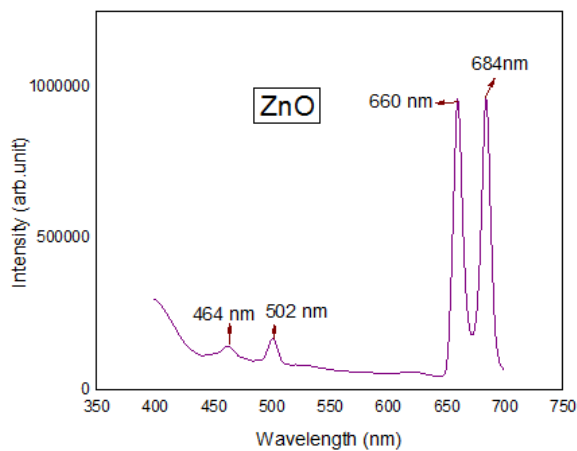


Figure 7: PL spectrum of ZnO nanoparticles

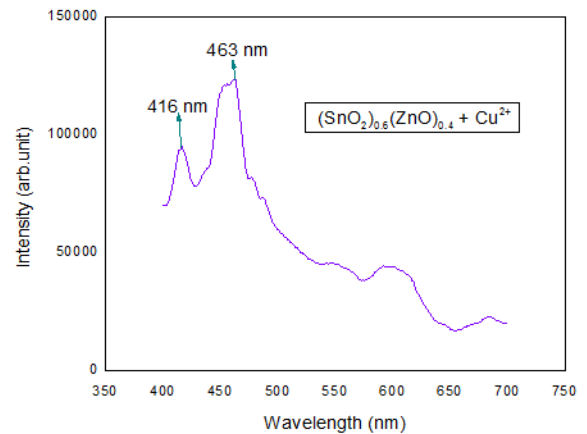
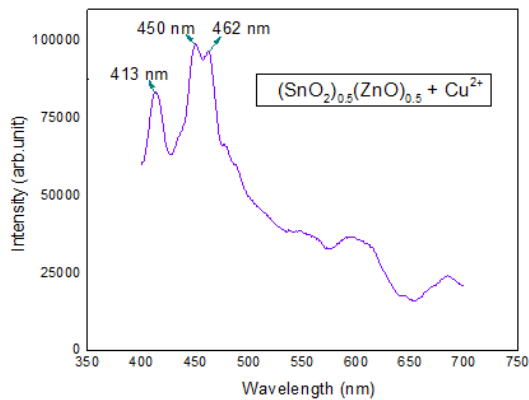
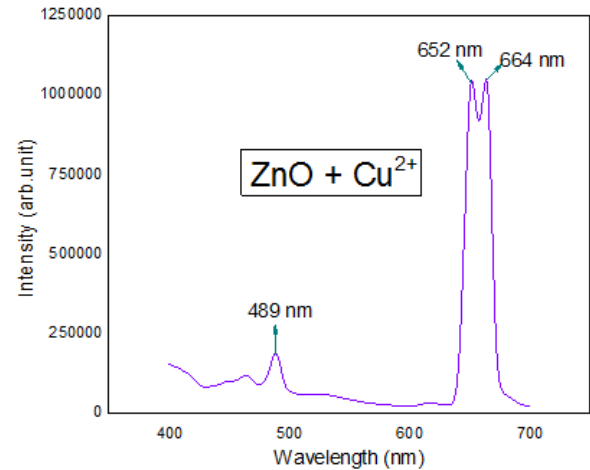
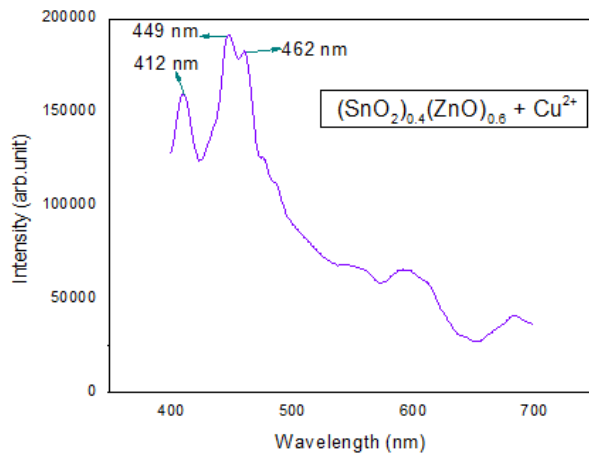
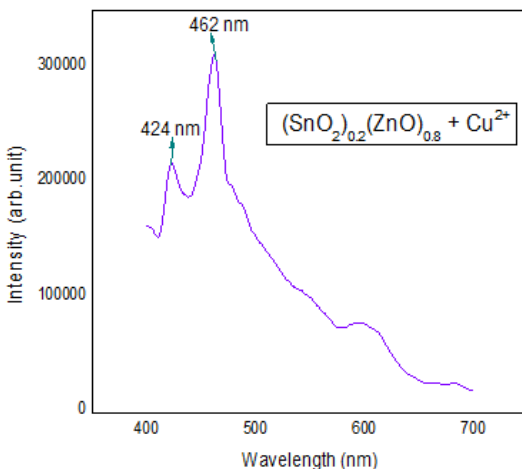


Figure 10: PL spectrum of  $(\text{SnO}_2)_{0.6}(\text{ZnO})_{0.4} + \text{Cu}^{2+}$  Nanocomposite

Figure 11: PL spectrum of  $(\text{SnO}_2)_{0.5}(\text{ZnO})_{0.5} + \text{Cu}^{2+}$  nanocompositeFigure 14: PL spectrum of  $\text{ZnO} + \text{Cu}^{2+}$  nanoparticlesFigure 12: PL spectrum of  $(\text{SnO}_2)_{0.4}(\text{ZnO})_{0.6} + \text{Cu}^{2+}$  nanocompositeFigure 13: PL spectrum of  $(\text{SnO}_2)_{0.2}(\text{ZnO})_{0.8} + \text{Cu}^{2+}$  nanocomposite

#### IV. CONCLUSION

The PL spectra of  $\text{SnO}_2$  nanoparticles show two prominent peaks at 421 and 462 nm.  $(\text{SnO}_2)_{1-x}(\text{ZnO})_x$  nanocomposites with  $x$  values (0.2, 0.4, 0.5, 0.6 and 0.8) show prominent peaks at 415 and 453 nm; 418 and 460 nm; 419 and 461 nm; 421 and 462 nm; 430 and 465 nm respectively. While  $\text{ZnO}$  nanoparticles show four prominent peaks at 464, 502, 660 and 684 nm respectively. Shifting in the peak position of  $\text{Cu}^{2+}$  doped  $(\text{SnO}_2)_{1-x}(\text{ZnO})_x$  nanocomposites when compared to undoped  $(\text{SnO}_2)_{1-x}(\text{ZnO})_x$  nanocomposites was observed. The shifting was mainly due to the incorporation of dopant into the host matrix and also it was coupled with the variation of band gap energies.

#### References

- [1]. M. A. Shah, Tokeer Ahmad, "Principles of Nanoscience and Nanotechnology", Narosa Publishing Houses Pvt, Ltd, New Delhi, 2010.
- [2]. R. Leghrib, E. Llobet, R. Pavelko, A. A. Vasiliev, A. Felten, J. J. Pireaux, "Gas sensing properties of MWCNTs decorated with gold or tin oxide nanoparticles", *Procedia Chemistry*, vol. 1, pp. 168–171, 2009.
- [3]. Kengo Shimano, Aya Nishiyama, Masayoshi Yuasa, Tetsuya Kida, Noboru Yamazoe, "Microstructure control of  $\text{WO}_3$  film by adding nano-particles of  $\text{SnO}_2$  for  $\text{NO}_2$  detection in ppb level", *Procedia Chemistry*, vol. 1, pp. 212–215, 2009.
- [4]. Artem Marikutsa, Valery Krivetskiy, Marina Rummyantseva, Elizaveta Konstantinova, Andrea Ponzoni, Elisabetta Comini, Alexander Gaskov, "Catalytic impact of  $\text{RuO}_x$  clusters to high  $\text{NH}_3$  sensitivity of tin dioxide", *Procedia Engineering*, vol. 25, pp. 227–230, 2011.
- [5]. Komol Kanta Sharker, A. Mubarak Khan, M. M. Shaik Khan, Rafiqul Islam, "Preparation and Characterization of Tin Oxide based Transparent Conducting Coating for Solar Cell Application", *Int. J. Thin. Fil. Sci. Tec.*, vol. 4, no. 3, pp. 243-247, 2015.
- [6]. Suphadate Sujinnapram, Sasimonton Moungrujun, "Additive  $\text{SnO}_2$ - $\text{ZnO}$  composite photoanode for improvement of power

- conversion efficiency in dye-sensitized solar cell”, *Procedia Manufacturing*, vol. 2, pp. 108 – 112, 2015.
- [7]. Nasibeh Shahrivar Fallah, Masoud Mokhtary, “Tin oxide nanoparticles (SnO<sub>2</sub>-NPs): An efficient catalyst for the one-pot synthesis of highly substituted imidazole derivatives”, *Journal of Taibah University for Science*, vol. 9, pp. 531–537, 2015.
- [8]. Manuela Stan, Adriana Popa, Dana Toloman, Adriana Dehelean, Ildiko Lung, Gabriel Katona, “Enhanced photocatalytic degradation properties of zinc oxide nanoparticles synthesized by using plant extracts”, *Materials Science in Semiconductor Processing*, vol. 39, pp. 23–29, 2015.
- [9]. Tamanna Bhuyan, Kavita Mishra, Manika Khanuja, Ram Prasad, Ajit Varma, “Biosynthesis of zinc oxide nanoparticles from *Azadirachta indica* for antibacterial and photocatalytic applications”, *Materials Science in Semiconductor Processing*, vol. 32, pp. 55–61, 2015.
- [10]. Jun Song Chen, Xiong Wen (David) Lou, “SnO<sub>2</sub> and TiO<sub>2</sub> nanosheets for lithium-ion batteries”, *Materials Today*, vol.15, no.6, pp. 246-254, 2012.
- [11]. Franziska Mueller, Dominic Bresser, Venkata Sai Kiran Chakravadhanula, Stefano Passerini, “Fe-doped SnO<sub>2</sub> nanoparticles as new high capacity anode material for secondary lithium-ion batteries”, *Journal of Power Sources*, vol. 299, pp. 398-402, 2015.
- [12]. Karzan Abdulkareem Omar, Bashdar Ismael Meena, Srwa Ali Muhammed, “Study on the activity of ZnO-SnO<sub>2</sub> nanocomposite against bacteria and fungi”, *Physicochem. Probl. Miner. Process*, vol. 52(2), pp. 754–766, 2016.
- [13]. Nasrin Talebian, Mohammad Reza Nilfroushan, Elahe Badri Zargar, “Enhanced antibacterial performance of hybrid semiconductor nanomaterials: ZnO/SnO<sub>2</sub> nanocomposite thin films”, *Applied Surface Science*, vol. 258, pp. 547– 555, 2011.
- [14]. Suresh Kumar, Ravi Nigam, Virender Kundu, Neena Jaggi, “Sol-gel synthesis of ZnO–SnO<sub>2</sub> nanocomposites and their morphological, structural and optical properties”, *J Mater Sci: Mater Electron*, 7 pages, 2015.
- [15]. Xiaohua Jia, Huiqing Fan, Lei Qin, Chao Yang, “Hierarchically Structure SnO<sub>2</sub>/ZnO Nanocomposites: Preparation, Growth Mechanism and Gas Sensing Property”, *Journal of Dispersion Science and Technology*, vol. 31, pp. 1405–1408, 2010.
- [16]. Prasopporn Junlabhut, Wanichaya Mekprasart, Russameeruk Noonuruk, Krisana Chongsri, Wisanu Pecharapa, “Characterization of ZnO:Sn nanopowders synthesized by co-precipitation method”, *Energy Procedia*, vol. 56, pp. 560 – 565, 2014.
- [17]. C. Kahattha, K. Chongsri, R. Noonuruk, W. Mekprasart, W. Pecharapa, “Effect of tin loading on physical properties and phase transformation of as-synthesized Zn-Sn-O compound powder synthesized by co-precipitation method”, *Energy Procedia*, vol. 56, pp. 673 – 677, 2014.
- [18]. Woon-Seop Choi, “Preparation of Zinc-tin-oxide Thin Film by Using an Atomic Layer Deposition Methodology”, *Journal of the Korean Physical Society*, vol. 57, no. 6, pp. 1472-1476, 2010.
- [19]. L. A. Patil, I. G. Pathan, D. N. Suryawanshi, A. R. Bari, D. S. Rane, “Spray pyrolyzed ZnSnO<sub>3</sub> nanostructured thin films for hydrogen Sensing”, *Procedia Materials Science*, vol. 6, pp. 1557 – 1565, 2014.
- [20]. R. H. Bari, S. B. Patil, A. R. Bari, “Chemically Sprayed Nanocomposite SnO<sub>2</sub>–ZnO Thin Film for Ethanol Gas Sensor”, *Journal of Nanoengineering and Nanomanufacturing*, vol. 3, pp. 1–5, 2013.
- [21]. K. J. Abhirama, K. U. Madhu, “Electrical Parameters of (SnO<sub>2</sub>)<sub>1-x</sub>(ZnO)<sub>x</sub> nanocomposites prepared by solvothermal method”, *International Journal of Advance Engineering and Research Development*, Volume 4, Issue 09, pp. 511-518, 2017.
- [22]. K. J. Abhirama, K. U. Madhu, “Synthesis and Electrical Characterization of Cu<sup>2+</sup> doped (SnO<sub>2</sub>)<sub>1-x</sub>(ZnO)<sub>x</sub> nanocomposites”, *Int. Journal of Engineering Research and Application*, Vol.7, Issue 11, Part -7, pp.64-72, 2017.
- [23]. N. Asama Naje, S. Azhar Norry, M. Abdulla Suhail, “Preparation and Characterization of SnO<sub>2</sub> Nanoparticles”, *International Journal of Innovative Research in Science, Engineering and Technology*, vol. 2, Issue 12, pp. 7068- 7072, 2013.
- [24]. M. Saravanakumar, S. Agila, N. Muthukumarasamy, V. Rukkumani, A. Marusamy, P. Uma mahshwari, A. Ranjitha, “Photoluminescence Studies on Nanocrystalline Pure and Cr Doped Tin Oxide Powder”, *Int.J. ChemTech Res*, vol. 6, no. 14, pp. 5429-5432, 2014.
- [25]. Nurul Syahidah Sabri, Mohd Salleh Mohd Deni, Azlan Zakaria, Mahesh Kumar Talari, “Effect of Mn Doping on Structural and Optical Properties of SnO<sub>2</sub> Nanoparticles Prepared by Mechanochemical Processing”, *Physics Procedia*, vol. 25, pp. 233 – 239, 2012.
- [26]. Xiaojuan Wu, Zhiqiang Wei, Lingling Zhang, Xuan Wang, Hua Yang, Jinlong Jiang, “Optical and Magnetic Properties of Fe doped ZnO Nanoparticles obtained by Hydrothermal Synthesis”, *Journal of Nanomaterials*, vol. 2014, 6 pages, 2014.
- [27]. Laishram Robindro Singh, “Photoluminescence Studies of ZnO, ZnO:Eu and ZnO:Eu Nanoparticles Covered with Y<sub>2</sub>O<sub>3</sub> Matrix”, *Materials Sciences and Applications*, vol. 6, pp. 269-278, 2015.
- [28]. Amita Verma, A. K. Srivastava, “Sol-gel derived nanostructured zinc oxide for bright luminescence in ultraviolet and visible spectral regions”, *Indian Journal of Chemistry*, vol. 50A, pp. 1697-1702, 2011.
- [29]. Elaheh Kowsari, Mohammad Reza Ghezelbash, “Ionic liquid-assisted, facile synthesis of ZnO/SnO<sub>2</sub> nanocomposites, and investigation of their photocatalytic activity”, *Materials Letters*, vol. 68, pp. 17–20, 2012.
- [30]. Satyanarayana Talam, Srinivasa Rao Karumuri, Nagarjuna Gunnam, “Synthesis, Characterization, and Spectroscopic Properties of ZnO Nanoparticles”, *ISRN Nanotechnology*, vol. 2012, 6 pages, 2012.
- [31]. K.Jeyasubramaniam, G.S. Hikku, R. Krishna Sharma, “Photocatalytic degradation of methyl violet dye using zinc oxide nanoparticles prepared by a novel precipitation method and its antibacterial activities”, *Journal of Water Process Engineering*, vol.8, pp. 35-44, 2015.
- [32]. Mehar Bhatnagar, Vishakha Kaushik, Akshey Kaushal, Mandeep Singh, Bodh Raj Mehta, “Structural and photoluminescence properties of tin oxide and tin oxide: C core-shell and alloy nanoparticles synthesised using gas phase technique”, *AIP Advances*, vol. 6, issue. 9, 12 pages, 2016.
- [33]. Edgar Mosquera, Carolina Rojas-Michea, Mauricio Morel, Francisco Gracia, Victor Fuenzalida, A.Ramón Zárate, “Zinc oxide nanoparticles with incorporated silver: Structural, morphological, optical and vibrational properties”, *Applied Surface Science*, vol. 347, pp. 561